


Look-Up Table for PVC Water Lines

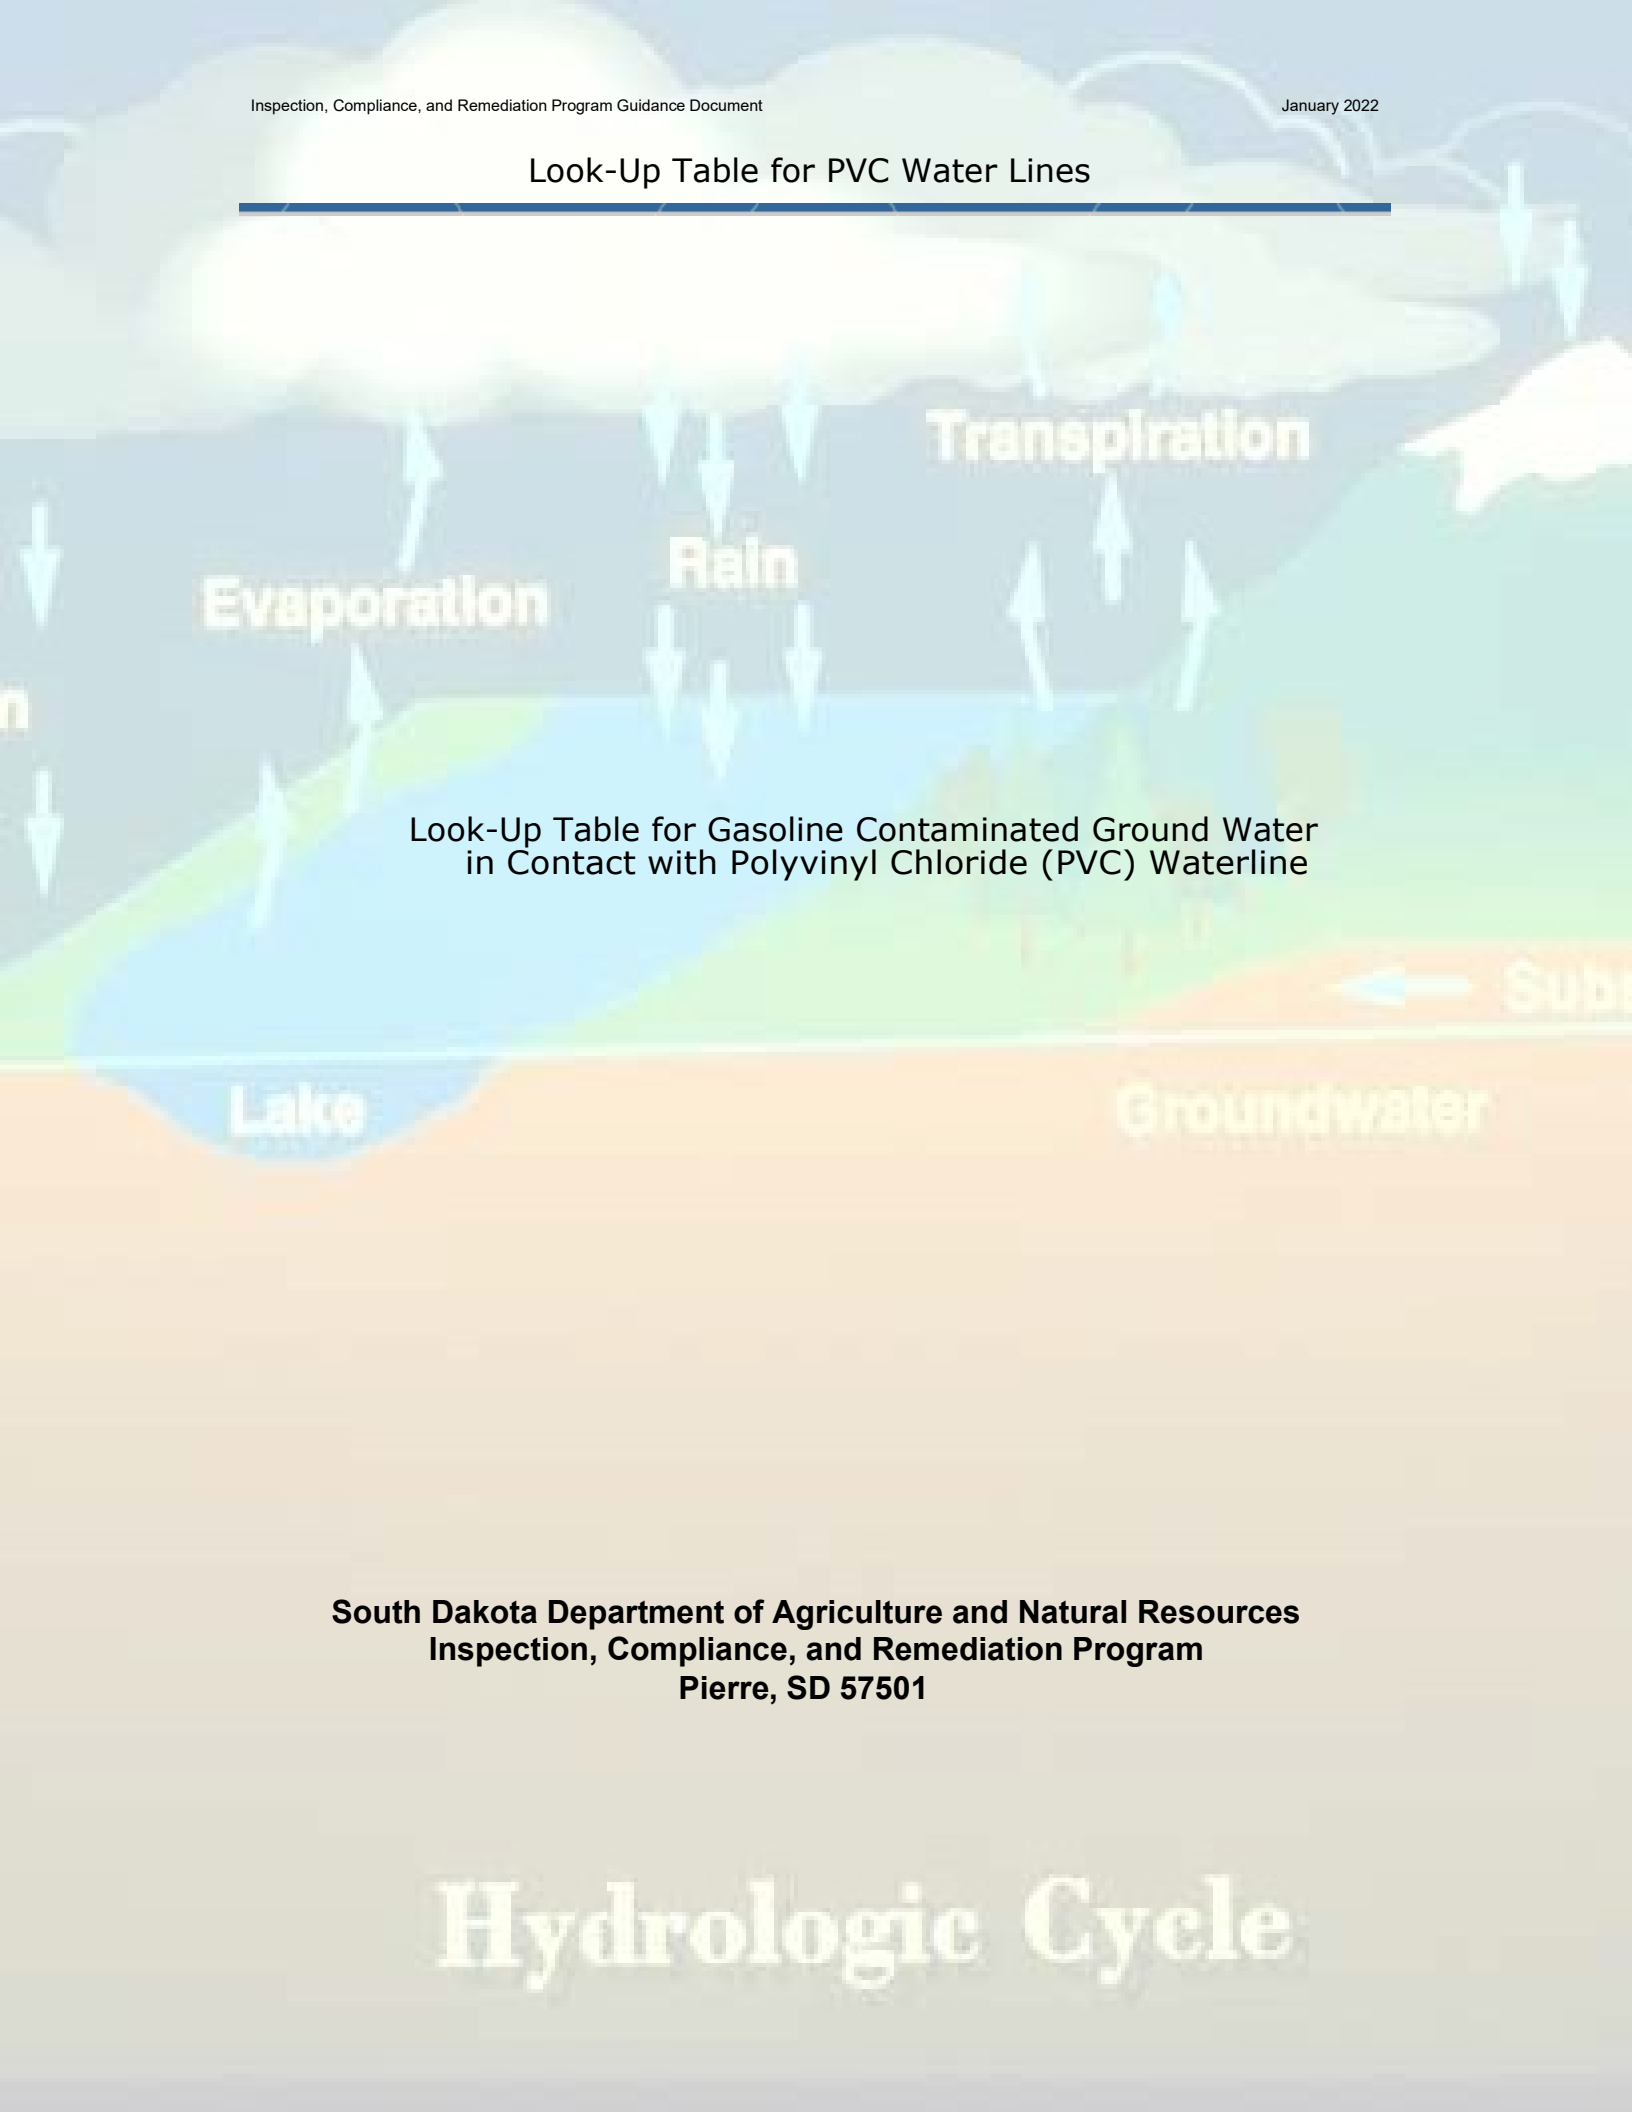

Look-Up Table for Gasoline Contaminated Ground Water
in Contact with Polyvinyl Chloride (PVC) Waterline

**South Dakota Department of Agriculture and Natural Resources
Inspection, Compliance, and Remediation Program
Pierre, SD 57501**

Hydrologic Cycle

**Look-Up Table for Gasoline Contaminated Ground Water in
Contact with Polyvinyl Chloride (PVC) Waterline**

Chemical of Concern ⁽¹⁾	Max. Solubility in Water (mg/l @ 20 ^o C) ⁽²⁾	Average % in Gasoline ⁽³⁾	Equilibrium Concentration in Ground Water (mg/l)	Activity ^{(4) (5)}	Maximum Allowable Concentration in Ground Water (mg/l)
Benzene	1780	1.8	32	0.1	3.2
Toluene	515	12.3	63	0.1	6.3

⁽¹⁾ Based on a review of the experimental literature for the permeation of polyvinyl chloride (PVC) pipe the Department believes that benzene and toluene represent the most concern, (i.e., softening of PVC).

⁽²⁾ Montgomery, John H., Welkom, Linda M., Groundwater Chemicals Desk Reference, (Chelsea, Michigan: Lewis Publishers, Inc.), 640 p., (1990).

⁽³⁾ W. Emile Coleman, Jean W. Munch, Robert P. Streicher, H. Paul Ringhand, and Frederick C. Koplner, 1984. The Identification and Measurement of Components in Gasoline, Kerosene, and No. 2 Fuel Oil that Partition into the Aqueous Phase after Mixing. Arch. Environ. Contam. Toxicol. 13, 171-178.

George P. Cross, 1971. Gasoline Composition and Vehicle Exhaust Gas Polynuclear Aromatic Content. Esso Research and Engineering Co., Linden, N.J., 124 p. PB 200-266

Harold E. Guard, James Ng, and Roy B. Loughlin, Jr., 1983. Characterization of Gasolines, Diesel Fuels, and Their Water Soluble Fractions. Naval Biosciences Laboratory, Oakland, CA, September 1983.

H.J. McDermott and S.E. Killiany, 1978. Quest for a Gasoline TLV. American Industrial Hygienists Association Journal 39, 110-117, February 1978.

National Research Council, 1981. The Alkyl Benzenes. National Academy Press, Washington, D.C.

W.N. Sanders and J.B. Maynard, 1968. Capillary Gas Chromatographic Method for Determining the C3 - C12 Hydrocarbons in Full-Range Motor Gasolines. Analytical Chemistry 40 (3), 527-535.

Mark E. Myers, Jr., Janis Stollsteiner, and Andrew M. Wims, 1975. Determination of Hydrocarbon Type-Distribution and Hydrogen/Carbon Ratio of Gasolines by Nuclear Magnetic Resonance Spectrometry. Analytical Chemistry pp(12), 2010-2015.

L.L. Stavinoha and F.M. Newman, 1972. The Isolation and Determination of Aromatics in Gasoline by Gas Chromatography. Journal of Chromatographic Science pp (9), 583-589.

- (4) Predictions regarding the possible permeation of an organic compound through plastic pipes should be based on the activity of that compound rather than the concentration. If possible, non-ideal effects in unsaturated organic vapors and in unsaturated aqueous solutions of organic compounds with low solubility can be neglected, the activity of an organic compound can be calculated quite simply in terms of concentration (Vonk, 1985):

$$a = C_w/C_{w,m}$$

with : a = activity (0=a=1)

C_w = concentration in water (mg/l)

$C_{w,m}$ = maximal solubility in water (mg/l)

- (5) The more conservative activity of 0.1 is being used since toluene may have slightly permeated PVC pipe at an activity of 0.11 in the laboratory experiments conducted by Vonk, 1985. In addition, since the synergistic effects of a mixture of gasoline constituents was not investigated in the laboratory experiments, the Department feels the more conservative activities are warranted for both constituents.

Note: The development of a look-up table for gasoline constituent (i.e., benzene, toluene, ethylbenzene, and xylenes) contaminated soil in contact with PVC waterlines is not feasible because it is necessary to know more site-specific information than just the concentration of the contaminants in soil. It has been shown that the relative organic chemical concentration in the soil pores controls the permeation rate. This requires the soil to be analyzed in such a way that the relative organic chemical concentration in the soil pores can be predicted. In order, to properly make this prediction site specific data such as soil organic carbon content, soil water content and soil porosity must be measured. For further discussion on the above analysis refer to the document published by the University of California at Berkley on Permeation of Plastic Pipes by Organic Chemicals, pages 303-305.

References:

Berens, A.R., Prediction of Organic Chemical Permeation Through PVC Pipes. Journal AWWA, 77:11:57 (November 1985).

Holsen, H.M., et al., The Effect of Soils on the Permeation of Plastic Pipes by Organics Chemicals. Journal AWWA, 83:11:85 (November 1991).

Selleck, R.E. & Marinas, J.M., Analyzing the Permeation of Organic Chemicals Through Plastic Pipes. Journal AWWA, 83:7:92 (July 1991).

Park, J.K., et al., Pipe Permeation Study, Final Report. Interagency Agreement 84/84371 between Department of Health Services, State of California, and the Regents of the University of California. Sanitary Engineering & Environmental Health Research Laboratory, University of California, Berkley (1989).

Vonk, M.W., Permeation of Organic Compounds Through Pipe Materials. Publication No. 85, the Netherlands Waterworks' Testing and Research Institute (KIWA), Neuwegein, the Netherlands (1985).